

Pushout Bond Strength of MTA as Root Canal Sealer: A Systematic Review

MANOJ CHANDAK¹, CHANCHAL RATHI², MADHULIKA CHANDAK³



ABSTRACT

Introduction: Endodontic treatment include different phases like controlling the growth of microorganism, thorough cleaning and shaping and fluid tight seal. Sealer plays an important role in root canal treatment. Sealer fills the space between filling material and dentin. Sealer also acts as a lubricant. Sealer has ability to fill the spaces and prevent microleakege from the root canal. Mineral Trioxide Aggregate (MTA) is a calcium silicate based sealer which has high radiopacity, low solubility and good antibacterial activity.

Aim: To evaluate pushout bond strength of MTA as a root canal sealer.

Materials and Methods: In this systematic review, the studies were chosen based on inclusion and exclusion criteria. Studies which were published in English, studies with different years of publication were included. Studies which includes bond strength of MTA as endodontic sealer to dentinal wall were also included. Studies used in this review were invitro studies and clinical trials. Studies showing tissue toxicity, biocompatibility of MTA were

excluded. Also, case reports and invivo studies were excluded. All abstracts as well as full texts were studied. PubMed/Medline, Web of Science, and Scopus were used for this study. Keywords used were “root canal sealer”, “pushout bond strength”, “MTA”. Total 18 articles were collected. But only five articles fulfilled the inclusion and exclusion criteria. So only five articles were included in this study and discussed in detail.

Results: According to the results of articles which were chosen for this study stated that MTA can be used as an endodontic sealer though it shows lesser pushout bond strength when compared with different newer sealers.

Conclusion: In this systematic review only one invitro study showed that Pro root MTA used as root canal sealer exhibits high pushout bond strength than other sealers like MTA Fillapex sealer and AH plus sealer. While MTA Fillapex show lesser pushout bond strength in comparison with other sealers like Pro root MTA sealer, AH plus, Endo CPM sealer. So this systematic review partially fulfills the hypothesis as it gives a utility of Pro root MTA as a root canal sealer.

INTRODUCTION

Successful endodontic treatment involves various steps like thorough cleaning and shaping as well as achieving complete three dimensional fluid tight seal. Filling material mainly consists of solid gutta percha [1]. This will occupy the canal space thoroughly. Sealer fills space between filling material and dentin [2]. Sealer also acts as a lubricant. Sealer have the ability to fill the spaces and prevent the microleakege from root canal. It should provide complete fluid tight seal [2]. It should not be harmful to the periapical tissues. It should help in healing of periapical lesions. Three-dimensional obturation requires for success of endodontic treatment. Also, success depends upon complete disinfection of pulpal canals [3]. Root canal sealers are categorised into zinc oxide eugenol containing sealer, calcium hydroxide containing sealer, calcium silicate containing sealer that is MTA sealer and resin containing sealer [4]. Newly introduced sealer is MTA sealer, MTA Fillapex “Angelus Solucxoes Odontologicas, Londrina, Brazil” that includes salicylates and resin. It also contains nano particulated resin, bismuth trioxide and MTA [4]. It is stated that it has more radiopacity and lesser solubility. It also shows lesser expansion while it sets [4]. It help to deposit the hard tissue [4]. Pushout test is the method which is used to measure the bond strength of endodontic filling material [5]. It provides knowledge about the adhesion properties of endodontic filling materials [5]. This test helps to evaluate the extent of bonding between sealer and dentin [5].

The prime purpose of this review was to evaluate the results of different studies which included the pushout bond strength of MTA based sealers. Hypothesis of this study is that MTA sealer has not sufficient amount of bond strength to root dentin when it is used as a sealer when compared with other sealers.

Keywords: Invitro studies, Pro root MTA, Review, Sealer

MATERIALS AND METHODS

The study was conducted in Sharad Pawar Dental College from the year 2019-2020 and it was completed within one year of duration.

Research Question

Is the pushout bond strength of MTA (MTA Fillapex) is higher than others sealers when it is used as a root canal sealer?

Procedure

This systematic review was prepared with the help of PRISMA chart. The studies were chosen based on inclusion and exclusion criteria. All abstracts as well as full texts were studied or screened by the author.

Inclusion Criteria

Studies which includes bond strength of MTA as endodontic sealer to dentinal wall were included. Studies used for this review are invitro studies and clinical trials. Different studies were chosen from year 2010-2019.

Exclusion Criteria

Study which showed tissue toxicity, biocompatibility of MTA were excluded. Also case reports and invivo studies were excluded to reduce the study bias.

Criteria for Selection of the Studies

Initially, title of the selected articles was read out. After that abstracts and full texts of that titles were read out. There was lack of retrospective and clinical trials. So this review incorporated only invitro studies. For this reason, Population, Intervention,

Comparison and Outcome (PICO) system were applied (Population: studies that demonstrate animal and human mesenchymal cells. Intervention includes study of the pushout bond strength of MTA sealer, Comparison (MTA), and Outcomes include bond strength of MTA to dentin).

Data Sources and Search Strategy


Pubmed/Medline, Web of Science, and Scopus were used for this study. During this procedure there was no restriction of years of publication.

To obtain more efficient results, authors searched the data sources using Medical Subject Headings (MeSH) terms. Keywords used were “MTA,” “root canal sealer,” “pushout bond strength” and “root dentin.” The search details were mineral trioxide aggregate (all fields) AND root canal sealer (all fields) AND pushout bond strength (All Fields).

Quality Assessment for Risk of Bias and Data Extraction

In second step full text of the chosen articles were read out for data extraction and quality assessment was done as per Office of Health Assessment and Translation (OHAT) tool by two independent reviewers (CR, MC). In cases of difference between reviewers, the third senior reviewer (MC) clarified the discrepancy.

Flow chart for this systematic review is shown in [Table/Fig-1]. In the beginning 18 articles were selected which includes pushout bond strength of MTA sealer only. Eleven studies which were based on cytotoxicity, biocompatibility of MTA were excluded. Also, three full text articles based on cytotoxicity and biocompatibility of MTA were excluded. Hence only four articles were selected (as shown in [Table/Fig-1]). Title, abstract, a scientific context based on pushout bond strength of MTA based sealer was included. Also rationale, objectives hypothesis, methodology showing study type were incorporated. Intrusion, statistical analysis, evaluation period were also used and main results were extracted from each experimental study.

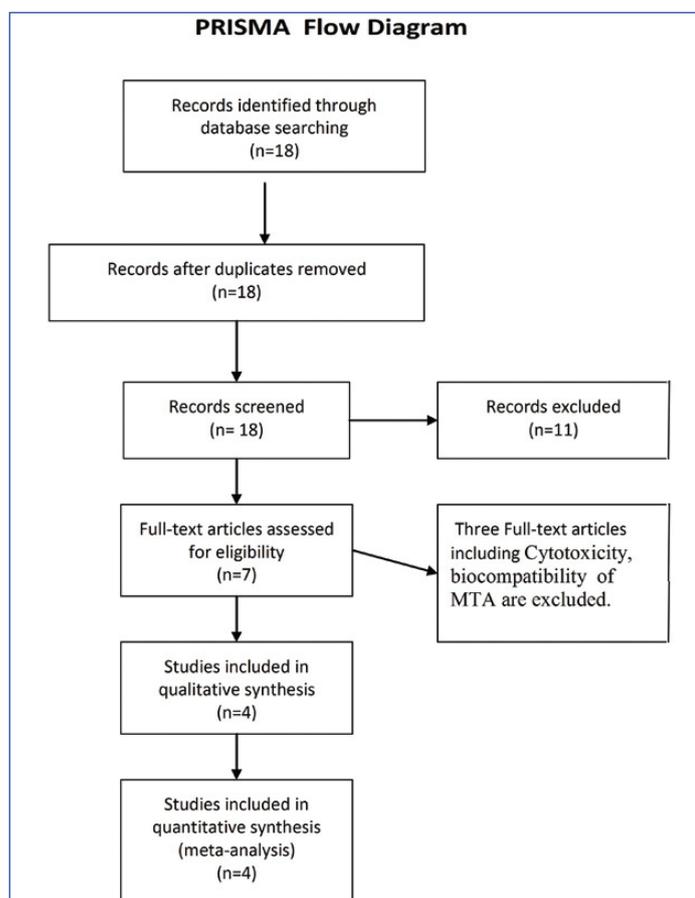

[Table/Fig-1]: Prisma flow diagram.

In this study, after quality assessment for risk of bias was done by three independent reviews and by OHAT tool, it was found that all studies included low risk of bias.

Quality assessment for risk of bias for invitro studies were done by OHAT tool as shown in [Table/Fig-2].

	Madhuri GV et al., [1]	Oliveira DS et al., [6]	Assmann E et al., [7]	Sönmez IŞ et al., [8]
Study group/ Samples allocation	40 samples randomly allotted (n=10) in four groups	60 samples randomly allotted (n=15) in four groups	45 samples randomly allotted (n=15) in three groups	30 samples randomly allotted (n=15) in three groups
Experimental conditions across study groups	No	No	No	No
Was research personnel blinded to the study groups	No	No	No	No
Were outcome data complete without attrition or exclusion from analysis	No	No	No	No
Can we confident in the outcome assessment (including blinding)	No	No	No	No

[Table/Fig-2]: Quality assessment for risk of bias for invitro studies was done by OHAT.

RESULTS

Initially, 18 articles were identified through database searching. Titles and abstracts were studied for initial screening. Full text was read out due to unclear results. The authors evaluated the studies, later discussed the results until a decision came out. Among the 18 studies, four were screened for inclusion. In these four articles only invitro studies were included. And remaining articles were excluded as they included cytotoxicity, biocompatibility. As a response to possible result established in PICO, MTA based sealer shows lower pushout bond strength compared to other sealers. Out of four invitro studies which were selected for this systematic review, all four studies showed that pushout bond strength of MTA Fillapex sealer was lesser compared to other sealers. While, one study shows Pro root MTA sealer shows better bond strength as compared to other sealers. This systematic review partially fulfills the hypothesis as it gives a utility of Pro root MTA as a root canal sealer According to [Table/Fig-3] first study which was given by Madhuri GV et al., resulted that Endosequence BC sealer showed higher pushout bond strength value, while MTA Fillapex showed lower pushout bond strength value [1].

In second study which was given by Oliveira DS et al., resulted that MTA showed higher bond strength value while MTA Fillapex shows lesser bond strength value [6].

In third study, which was given by Assmann E et al., resulted in the MTA Fillapex showing lesser bond strength value as compared to other sealers [7].

In the fourth study, which was given by Sönmez IŞ et al., resulted in Pro root MTA had the highest bond strength, whilst MTA Fillapex displayed the lowest values among the groups [8]. So, [Table/Fig-3] represents the comparison of pushout bond strength of MTA based sealer with other different sealers.

Risk of Bias in Included Studies

In this systematic review four studies were included. Quality assessment for risk of bias was done by OHAT tool as shown in [Table/Fig-2]. In all the four studies by Madhuri GV et al., Oliveira DS et al., Assmann E et al., and Sönmez IŞ et al., samples were allocated randomly [1,6,7,8]. In all the four studies pushout bond strength was checked by universal testing machine. But in all the studies different sealers were used. So after quality assessment for risk of bias, it was concluded that there was a chance of presence of low risk of bias in all the four studies.

First author	Year	Type of study	Sample size	Comparative material	Pushout Bond Strength (MPa)	Results	Conclusion
Madhuri GV et al., [1]	2016	Invitro study	40 single rooted human teeth	MTA Fillapex sealer with hybrid root seal, endosequence bioceramic sealer, epoxy resin based sealer.	MTA Fillapex=30.39 Hybrid root seal=51.89 Bioceramic endosequence sealer=98.72 Epoxy resin based sealer (MM seal)=71.69	The more bond strength were shown in Group 1 "Endosequence- $p<0.05$ " when compared with others. Lesser bond strength were shown in Group 2.	Endosequence BC sealer showed higher pushout bond strength value compared to other sealers. Lowest bond strength was seen with MTA Fillapex sealer.
Oliveira DS et al., [6]	2015	Invitro study	60 single rooted human teeth	MTA Fillapex I Root sp MTA AH Plus	MTA Fillapex=2.00 I root sp=2.9 MTA=9.3 AH plus=8.02	MTA-filled Samples had the better bond strength " $p=0.000$ ". AH Plus had significantly better bond strength compared to group I, group II ($p=0.000$). Both group I, group II were shown lesser bond strength compared to others.	The adhesion to root dentine associated with newer calcium silicate-based sealers was compromised even when well-monitored laboratory conditions were used.
Assmann E et al., [7]	2012	Invitro study	45 single rooted human teeth	AH plus sealer MTA Fillapex Endo-CPM sealer.	Endo-CPM =8.26 AH plus=3.03 MTA Fillapex=2.04	The Endo-CPM sealer showed more bond strength compared with the others. No difference were found between the AH Plus as well as the MTA Fillapex	On the basis of the findings presented herein and within the limitations of this study, Endo-CPM sealer presented advantages when a post preparation was required. MTA Fillapex presented acceptable resistance to dislodgement, which was similar to that observed in samples filled with AH Plus sealer.
Sönmez IŞ et al., [8]	2013	Invitro study	30 single rooted human teeth	AH plus sealer Pro root MTA MTA Fillapex	AH plus=1.27 Pro root MTA=4.07 MTA Fillapex=0.46	Pushout bond strength of group II was better than AH Plus. Group II showed better bond strength compared to group III.	Pro root MTA had the highest bond strength, whilst MTA Fillapex displayed the lowest values among the groups.

[Table/Fig-3]: Represents the comparison of pushout bond strength of MTA based sealer. with other different sealers [1,12,13,15].

DISCUSSION

For the success of endodontic treatment complete filling of root canal is utmost important to avoid reinfection [1]. It is also important to remove the viable bacteria which cause infection [3]. Sealer fills the space between filling material and dentin [9]. It also fills the space among the core material as well as the accessory canal [9]. It also acts as a lubricant. Ultimately, it helps in achieving three dimensional seal [10]. In any clinical scenario, adhesion is mandatory to evade dislocation of sealer [10].

Pushout test is the method which helps to evaluate the bond strength among sealers as well as dentinal walls [1]. This test is based on the stresses which are generated between root dentine and cement. The force is applied from coronal to apical direction [1]. Force will be applied till the filling material is dislodged from the canals [2]. This testing method completely replicates the performance of sealer [11]. And, it also provides information which can be a useful tool for comparison of different endodontic sealers or obturation techniques [1]. Few studies were conducted to compare the biocompatibility and sealing ability of MTA and other routine sealers, which includes calcium hydroxide based, zinc oxide eugenol based sealers [12]. Also, resins based sealers and bioceramic sealer were included in the comparison [13,14]. Till date, there were no systematic reviews are present based on pushout bond strength of MTA as an endodontic sealer.

The various studies conducted have stated following results of using MTA as an endodontic sealer.

Madhuri GV et al., stated that MTA Fillapex had shown lesser bond strength compared to Endosequence (bioceramic) sealer, hybrid root seal as well as MM seal. It is because of release of calcium ion. It also releases hydroxyl ions from the set sealer which forms tag like structures. This tag like structure interferes with bonding of endodontic sealer with root dentin. So it has lesser amount of bond strength [1].

Oliveira DS et al., stated that MTA sealer showed highest bond strength. Because it can seal the entire root canal space as it consists of MTA powder or hydrophilic powder. Water is required for its setting and formation of a hydrocolloid gel [6]. This gel hardens

after some period of time and form strong impermeable barrier within four weeks. This setting ability of MTA gives its high strength [5].

Assmann E et al., stated that MTA Fillapex show less pushout bond strength than Endo-CPM and AH plus sealer. It is because tag like structure formed by MTA Fillapex. It will form by releasing calcium and hydroxyl ions during its setting reaction. This tag like structure interferes with bonding between sealer and core material (gutta percha) as well as sealer and dentin [7].

Sagsen B et al., studied in 2011 that MTA Fillapex has lowest pushout bond strength. This is due to release of calcium and hydroxyl ions by the set sealer [15], which will ultimately form tag like structures. This tag like structure interferes with bonding of sealer with root dentin so it shows lowest bond strength [8].

Sönmez IŞ et al., stated that Pro root MTA showed highest pushout strength in comparison with AH plus as well as MTA Fillapex sealer [8]. Sealers are binding agents used to fill up the gap between root canal wall and obturating material [16]. Pro Root MTA sealer helps to seal whole canal space. It is because of hydrophilic powder present in MTA which sets in presence of water [8].

Limitation(s)

Few clinical trials and invivo studies are present on use of MTA as a root canal sealer. So in this systematic review articles chosen were less. So there is a chance of error in the results. So, more studies on the use of MTA as root canal sealer are required.

CONCLUSION(S)

In this systematic review one invitro study showed that when Pro root MTA used as a root canal sealer it exhibited high pushout bond strength than other sealers like MTA Fillapex sealer and AH plus sealer. While MTA Fillapex show lesser pushout bond strength in comparison with other sealers. So according to this review MTA is used as a root canal sealer as it exhibit better pushout bond strength compared to other sealers. But further clinical trials, invivo studies are required to study the application of MTA as an endodontic sealer in terms of their pushout bond strength.

REFERENCES

- [1] Madhuri GV, Varri S, Bolla N, Mandava P, Akkala LS, Shaik J. Comparison of bond strength of different endodontic sealers to root dentin: An invitro push-out test. *Journal of conservative dentistry: JCD*. 2016;19(5):461.
- [2] Zhang W, Li Z, Peng B. Assessment of a new root canal sealer's apical sealing ability. *Oral Surgery, Oral Medicine, Oral Pathology, Oral Radiology, and Endodontology*. 2009;107(6):e79-82.
- [3] DeLong C, He J, Woodmansey KF. The effect of obturation technique on the push-out bond strength of calcium silicate sealers. *Journal of Endodontics*. 2015;41(3):385-88.
- [4] Shokouhinejad N, Hoseini A, Gorjestani H, Shamsiri AR. The effect of different irrigation protocols for smear layer removal on bond strength of a new bioceramic sealer. *Iranian Endodontic Journal*. 2013;8(1):10.
- [5] De Oliveira NG, de Souza Araújo PR, da Silveira MT, Sobral AP, de Vasconcelos Carvalho M. Comparison of the biocompatibility of calcium silicate-based materials to mineral trioxide aggregate: Systematic review. *European Journal of Dentistry*. 2018;12(02):317-26.
- [6] Oliveira DS, Cardoso ML, Queiroz TF, Silva EJ, Souza EM, De-Deus G. Suboptimal push-out bond strengths of calcium silicate-based sealers. *International Endodontic Journal*. 2016;49(8):796-801.
- [7] Assmann E, Scarparo RK, Böttcher DE, Grecca FS. Dentin bond strength of two mineral trioxide aggregate-based and one epoxy resin-based sealers. *Journal of Endodontics*. 2012;38(2):219-21.
- [8] Sönmez İŞ, Sönmez D, Almaz ME. Evaluation of push-out bond strength of a new MTA-based sealer. *European Archives of Paediatric Dentistry*. 2013;14(3):161-66.
- [9] Gade VJ, Belsare LD, Patil S, Bhede R, Gade JR. Evaluation of push-out bond strength of endosequence BC sealer with lateral condensation and thermoplasticized technique: An invitro study. *Journal of Conservative Dentistry: JCD*. 2015;18(2):124.
- [10] Gurgel-Filho ED, Leite FM, Lima JB, Montenegro JP, Saavedra F, Silva EJ. Comparative evaluation of push-out bond strength of a MTA-based root canal sealer. *Brazilian Journal of Oral Sciences*. 2014;13(2):114-17.
- [11] Setia P, Sikri VK, Sroa RB, Sidhu B. Apical sealing ability of two novel root canal sealers: An ex-vivo study. *Journal of the International Clinical Dental Research Organization*. 2013;5(1):9.
- [12] Barbizam JV, Trope M, Tanomaru-Filho M, Teixeira EC, Teixeira FB. Bond strength of different endodontic sealers to dentin: Push-out test. *Journal of Applied Oral Science*. 2011;19(6):644-47.
- [13] Patni PM, Chandak M, Jain P, Patni MJ, Jain S, Mishra P, et al. Stereomicroscopic evaluation of sealing ability of four different root canal sealers-an invitro study. *Journal of Clinical and Diagnostic Research: JCDR*. 2016;10(8):ZC37.
- [14] Reyhani MF, Ghasemi N, Rahimi S, Milani AS, Mokhtari H, Shakouie S, et al. Push-out bond strength of Dorifill, Epiphany and MTA-Fillapex sealers to root canal dentin with and without smear layer. *Iranian Endodontic Journal*. 2014;9(4):246.
- [15] Sagsen B, Ustün Y, Demirbuga S, Pala K. Push-out bond strength of two new calcium silicate-based endodontic sealers to root canal dentine. *International Endodontic Journal*. 2011;44(12):1088-91.
- [16] Chandak M, Salgar A, Nikhade P, Shrivastava S, Sahni A, Chandak R. Comparative evaluation of efficacy and effectiveness of profile rotary instruments in conjugation with solvent for retreatment of resilon and gutta-percha: An Invitro study. *Journal of Datta Meghe Institute of Medical Sciences University*. 2017;12(2):115.

PARTICULARS OF CONTRIBUTORS:

1. Professor, Department of Conservative Dentistry and Endodontics, Sharad Pawar Dental College and Hospital, Datta Meghe Institute of Medical Sciences, Deemed to be University (DU), Sawangi, Wardha, Maharashtra, India.
2. Postgraduate Student, Department of Conservative Dentistry and Endodontics, Sharad Pawar Dental College and Hospital, Datta Meghe Institute of Medical Sciences, Deemed to be University (DU), Sawangi, Wardha, Maharashtra, India.
3. Postgraduate Student, Department of Conservative Dentistry and Endodontics, Sharad Pawar Dental College and Hospital, Datta Meghe Institute of Medical Sciences, Deemed to be University (DU), Sawangi, Wardha, Maharashtra, India.

NAME, ADDRESS, E-MAIL ID OF THE CORRESPONDING AUTHOR:

Dr. Manoj Chandak,
SPDC, Sawangi, Wardha, Maharashtra, India.
E-mail: drmanojchandak@yahoo.com

PLAGIARISM CHECKING METHODS: [Jain H et al.]

- Plagiarism X-checker: Apr 11, 2020
- Manual Googling: Jul 02, 2020
- iThenticate Software: Sep 28, 2020 (11%)

ETYMOLOGY: Author Origin

AUTHOR DECLARATION:

- Financial or Other Competing Interests: None
- Was informed consent obtained from the subjects involved in the study? No
- For any images presented appropriate consent has been obtained from the subjects. No

Date of Submission: **Apr 10, 2020**

Date of Peer Review: **May 18, 2020**

Date of Acceptance: **Jul 10, 2020**

Date of Publishing: **Oct 01, 2020**